

TECH MEMO

TECHNICAL MEMORANDUM 43-19

SURFACE EFFECTS IN ALKALI-HALIDE CRYSTALS RESULTING FROM IRRADIATION BY X-RAYS

J. B. Bernstein, D. D. Kirk, and D. L. Stierwalt

Infrared Division, Research Department

FACILITY FORM 602

N65-23332

(ACCESSION NUMBER)

(THRU)

10
(PAGES)

1
(CODE)

CR 62617
(NASA CR OR TMX OR AD NUMBER)

26
(CATEGORY)

NAVAL ORDNANCE LABORATORY CORONA

CORONA, CALIFORNIA

19208
Hard copy (HC) \$ 1.00

Microfiche (MF) .50

December, 1964

NAVAL ORDNANCE LABORATORY CORONA

E. B. JARMAN, CAPT., USN
Commanding Officer

F. S. ATCHISON, Ph. D.
Technical Director

FOREWORD

The research reported here was conducted in the Infrared Division of the Research Department, NOLC, with funds supplied by the National Aeronautics and Space Administration Purchase Order No. W-11, 400-B.

ROY F. POTTER
Head, Infrared Division

ABSTRACT

The spectral emittance at 373°K of some alkali-halide crystals was measured before and after irradiation by 50-kilovolt 50-milliampere x-rays.

INTRODUCTION

Chemical reactions occur at room temperature between crystalline NaCl and some components of the atmosphere.^{1,2} In addition to the formation of carbonates, unpublished data obtained at the Lewis Research Center show that nitrate (NO_3^-) or nitrite (NO_2^-) ions are produced on a surface of NaCl crystals exposed to air in the presence of an electric spark, X-irradiation, or α bombardment.

23332 ABST
This report, without attempting to differentiate between the above chemical reactions, shows some of the results of exposing a series of alkali-halides to X-irradiation and measuring a resulting change in the absorptance spectra of the crystals. The technique employed to examine the crystals is the measurement of their spectral emittance before and after their exposure to X-irradiation.

The theory, techniques and experimental apparatus used in acquiring the spectral emittance (spectral absorptance) of a transparent solid, in the infrared region of the spectrum, have been discussed in detail in previous reports.^{3,4} It should be noted that the spectral emittance measurement technique represents a direct measure of absorptance. A transmittance measurement would need a supplementary reflectance measurement to determine the spectral absorptance.

The crystals measured are KCl ($t = 2.10$ mm), RbBr ($t = 5.31$ mm), NaCl ($t = 6.56$ mm) and KBr ($t = 4.65$ mm).

AUTHOR

RESULTS

Figures 1a, 2a, 3a, and 4a show the spectral emittances at 373°K of curves NaCl, KBr, RbBr, and KCl respectively.

Figures 1b, 2b, 3b, and 4b show respectively the spectral emittances at 373°K of NaCl after two hours of x-ray irradiation, KBr after six hours irradiation, RbBr after three hours irradiation and KCl after two hours irradiation. Samples were irradiated in the atmosphere at 25°C with a Macklet AEG50S tungsten target, unfiltered. An additional sample of NaCl crystal, enclosed in a nitrogen atmosphere was irradiated. At the completion of the emittance measurements, a surface layer of 0.04 mm was removed from the face of NaCl, 0.05 mm from the face of the KCl and 0.1 mm removed from the face of RbBr. The spectral emittances of these three samples, which had been irradiated in the atmosphere, were measured again, with the result that all the structure in the 7.0 - 7.3 micron region, which appeared after irradiation, had disappeared. The sample irradiated in the nitrogen atmosphere showed no change in structure due to irradiation. Because of the deterioration of the crystal, the KBr sample was not remeasured after removal of the surface layer.

CONCLUSIONS

No attempt is made here to quantitatively establish the exact mechanism, or to identify the resulting surface changes. It is evident, however, that X-irradiation of the sample in a pure nitrogen atmosphere does not produce this effect in the 7.0 - 7.3 micron region. It does not exclude the possibility, however, that nitrogen

in combination with other atmospheric gases may produce this surface change. There is evidence⁵, however, which points to the possibility that the formation of carbonates takes place at/and near the surface of the crystal during X-irradiation in the presence of atmospheric CO₂.

This, the initial experiment using the spectral emittance technique at low temperatures to observe these surface changes in the alkali-halide crystals, provides an excellent tool for correlating the results of measurements made by mass spectrometric and microchemical analysis techniques.^{1,2}


DISCUSSION

The following experiments, using the "spectral emittance techniques", should be considered for future development of surface effect studies of the type described in this report.

1. The quantitative measurement of depth of penetration of chemical change as a function of irradiation time, intensity and energy.
2. Effects of ultra violet and gamma radiation.
3. Irradiation effect in the presence of atmospheric gases individually and in combination.
4. Correlate emittance measurements with mass spectrometer studies in a program for identifying the chemical species.

BIBLIOGRAPHY

1. Otterson, Dumas A. Influence of Room Temperature Atmospheric Reaction Products on the Quality of Sodium Chloride Single Crystals, J. Chem. Phys. 38, 1481-1485 (1963).
2. Otterson, Dumas A. and Davies, Myron O., Study of Carbonate Impurity in Surface Region of Sodium Chloride Crystals, NASA Technical Note D-2434, August 1964.
3. Stierwalt, D. L. Kirk, D. D., and Bernstein, J. B. An Instrument for Measuring the Spectral Emittance of a Solid in the Infrared from 16 to 45 Microns at Low Temperature, NOLC Report 589, Aug. 1963.
4. NAVWEPS Report 7160, Infrared Spectral Emissivity of Optical Materials, D. L. Stierwalt, 15 January 1961 (NOLC 537).

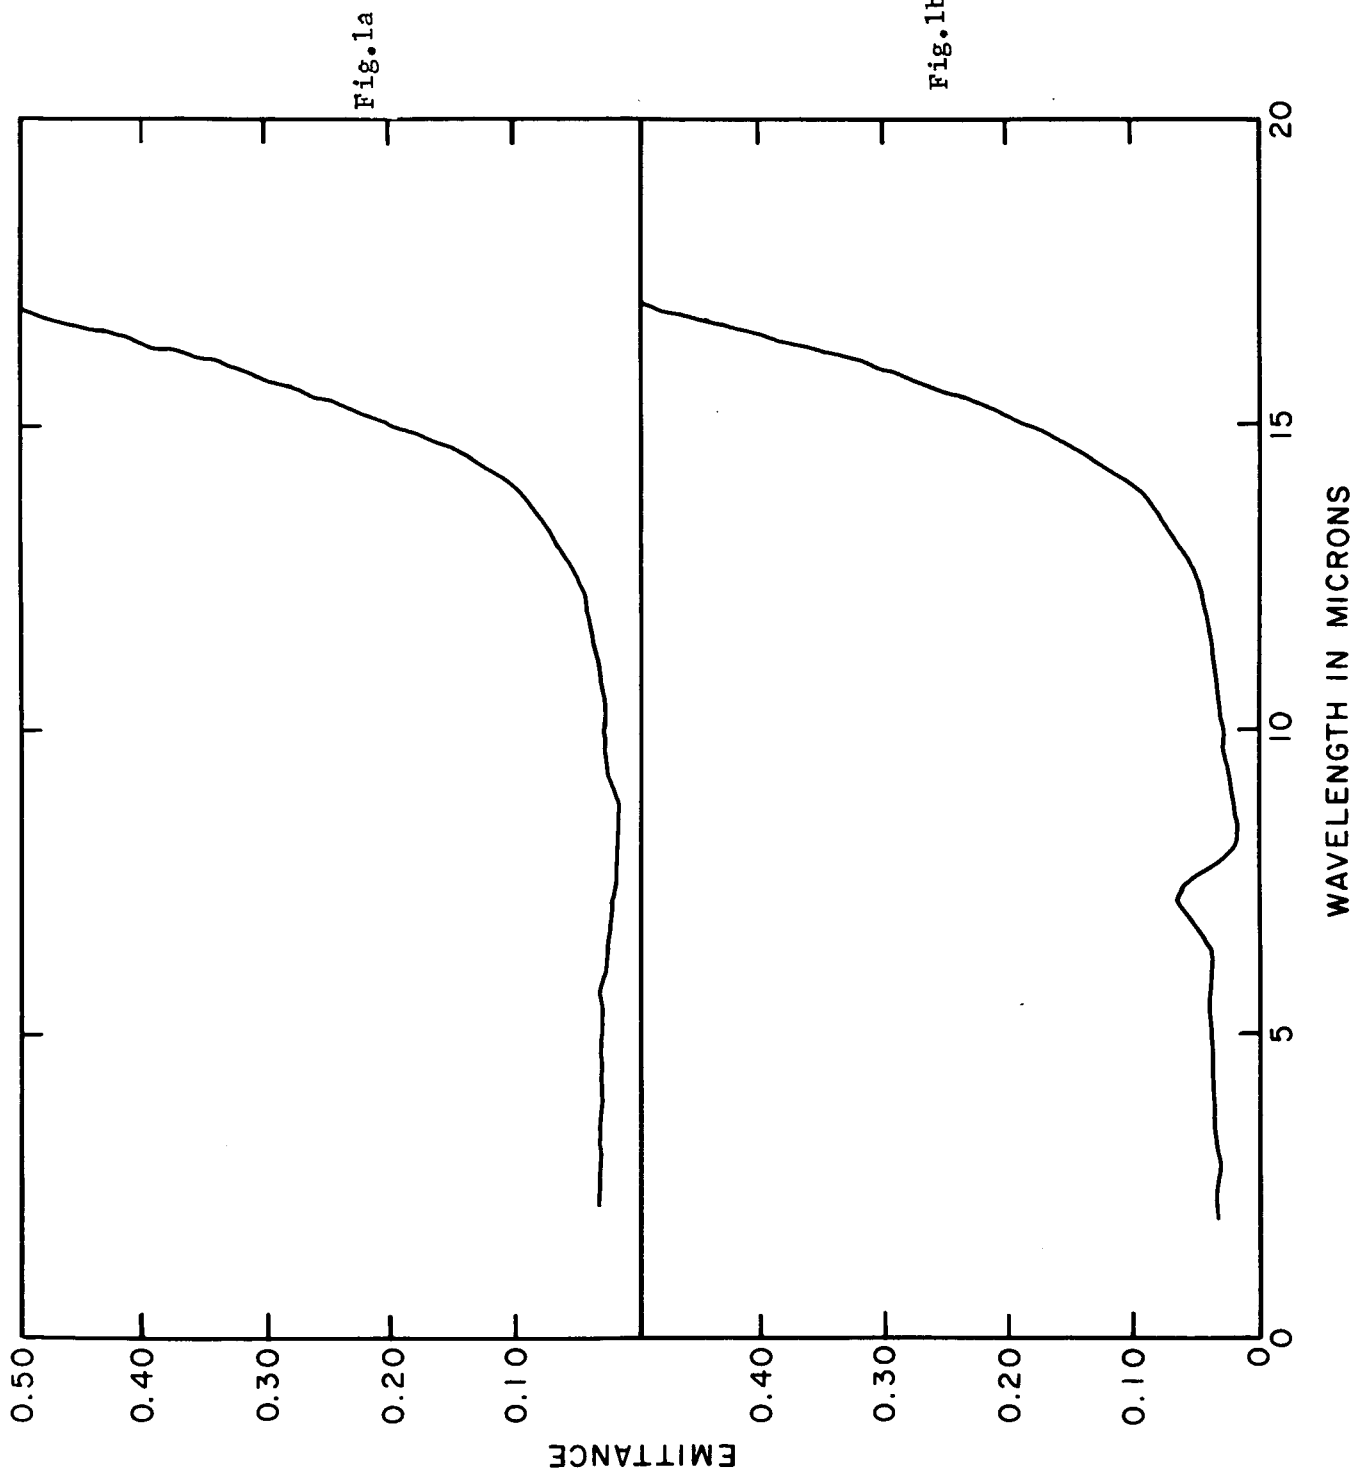

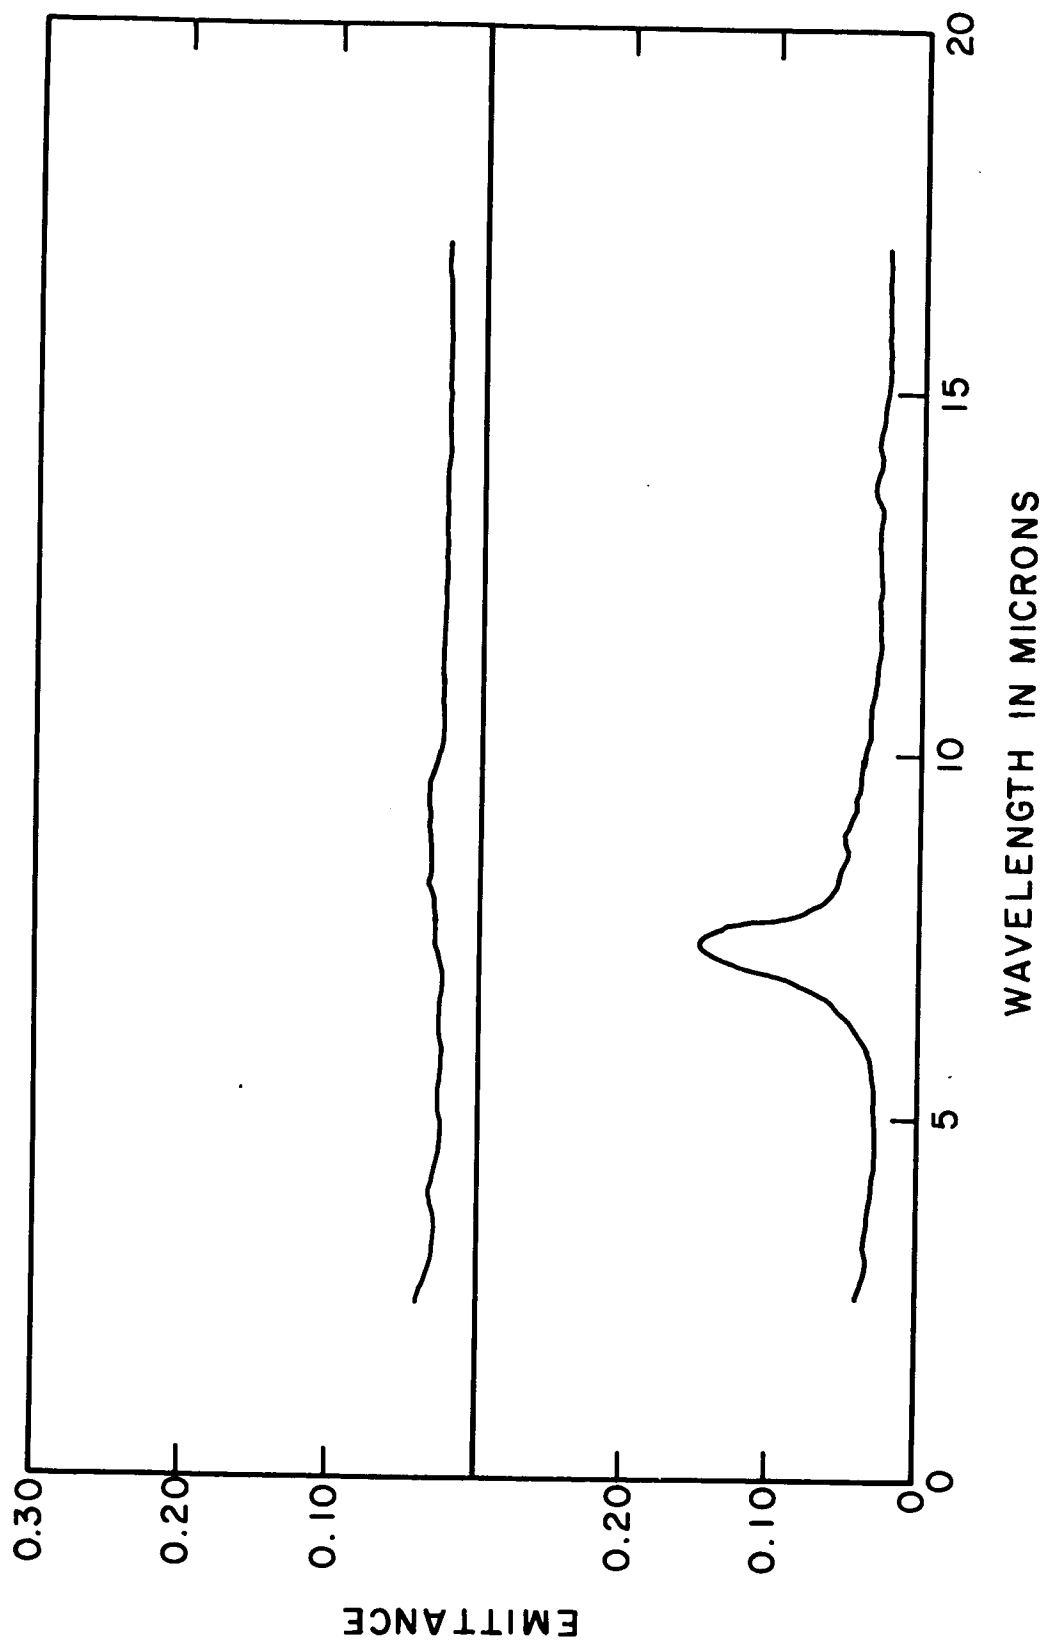


Fig. 2b

Fig. 2a


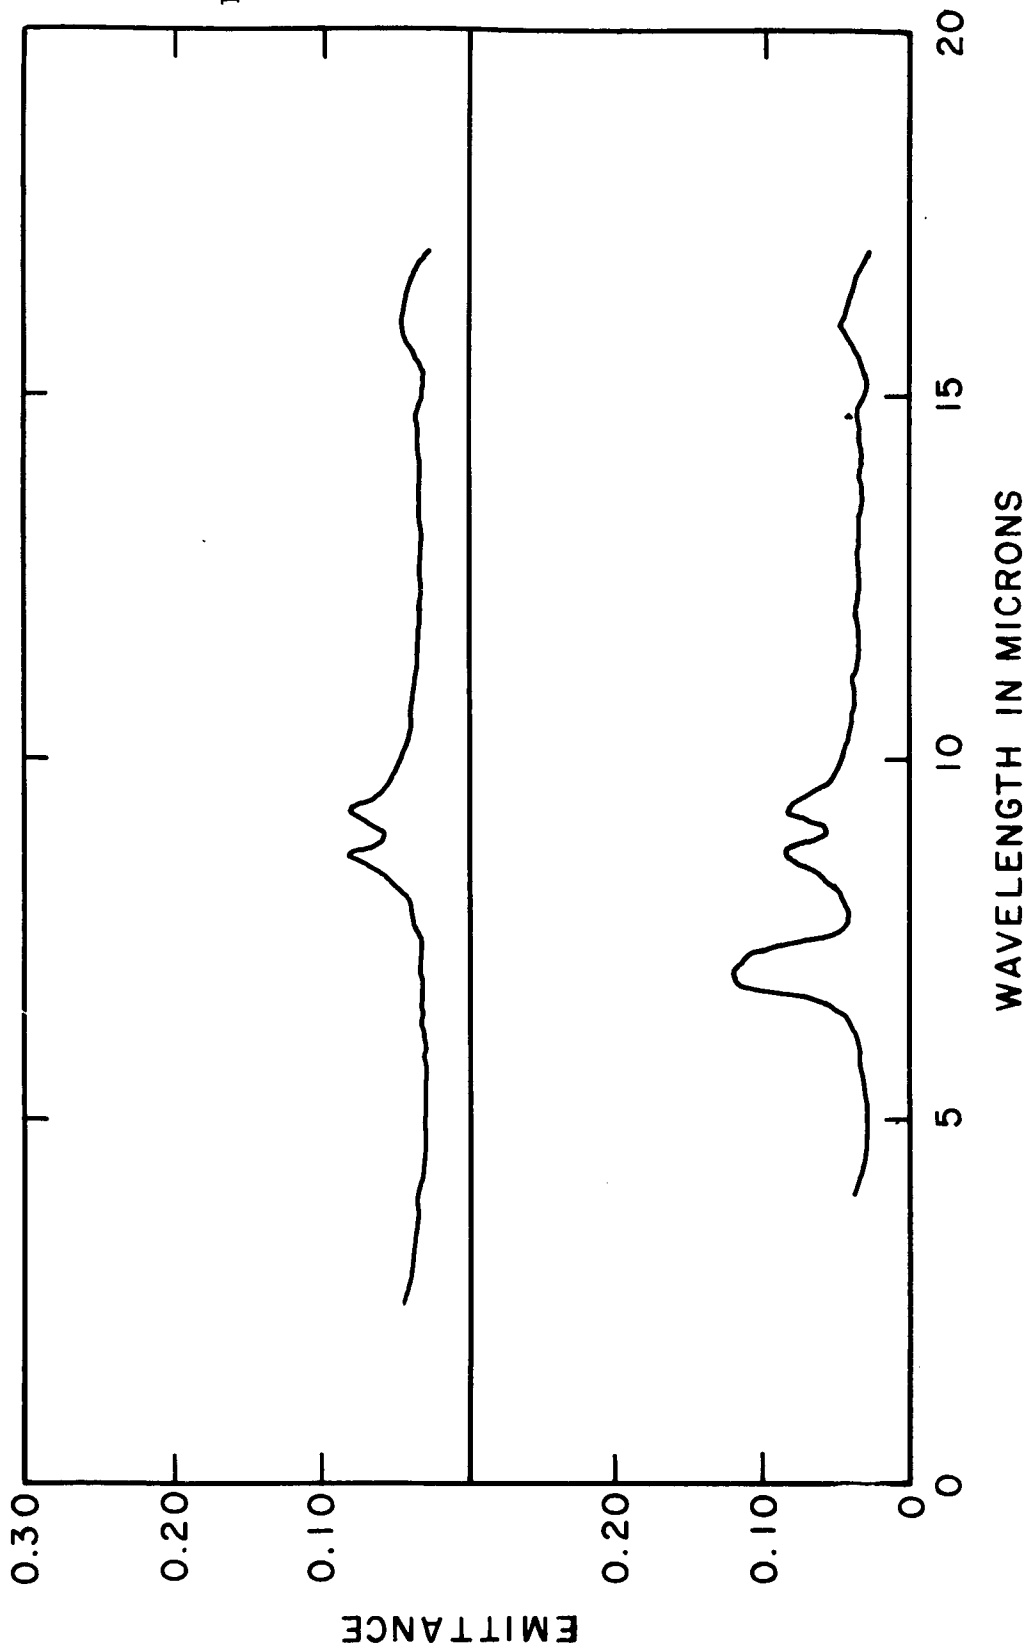


Fig. 3a

Fig. 3b

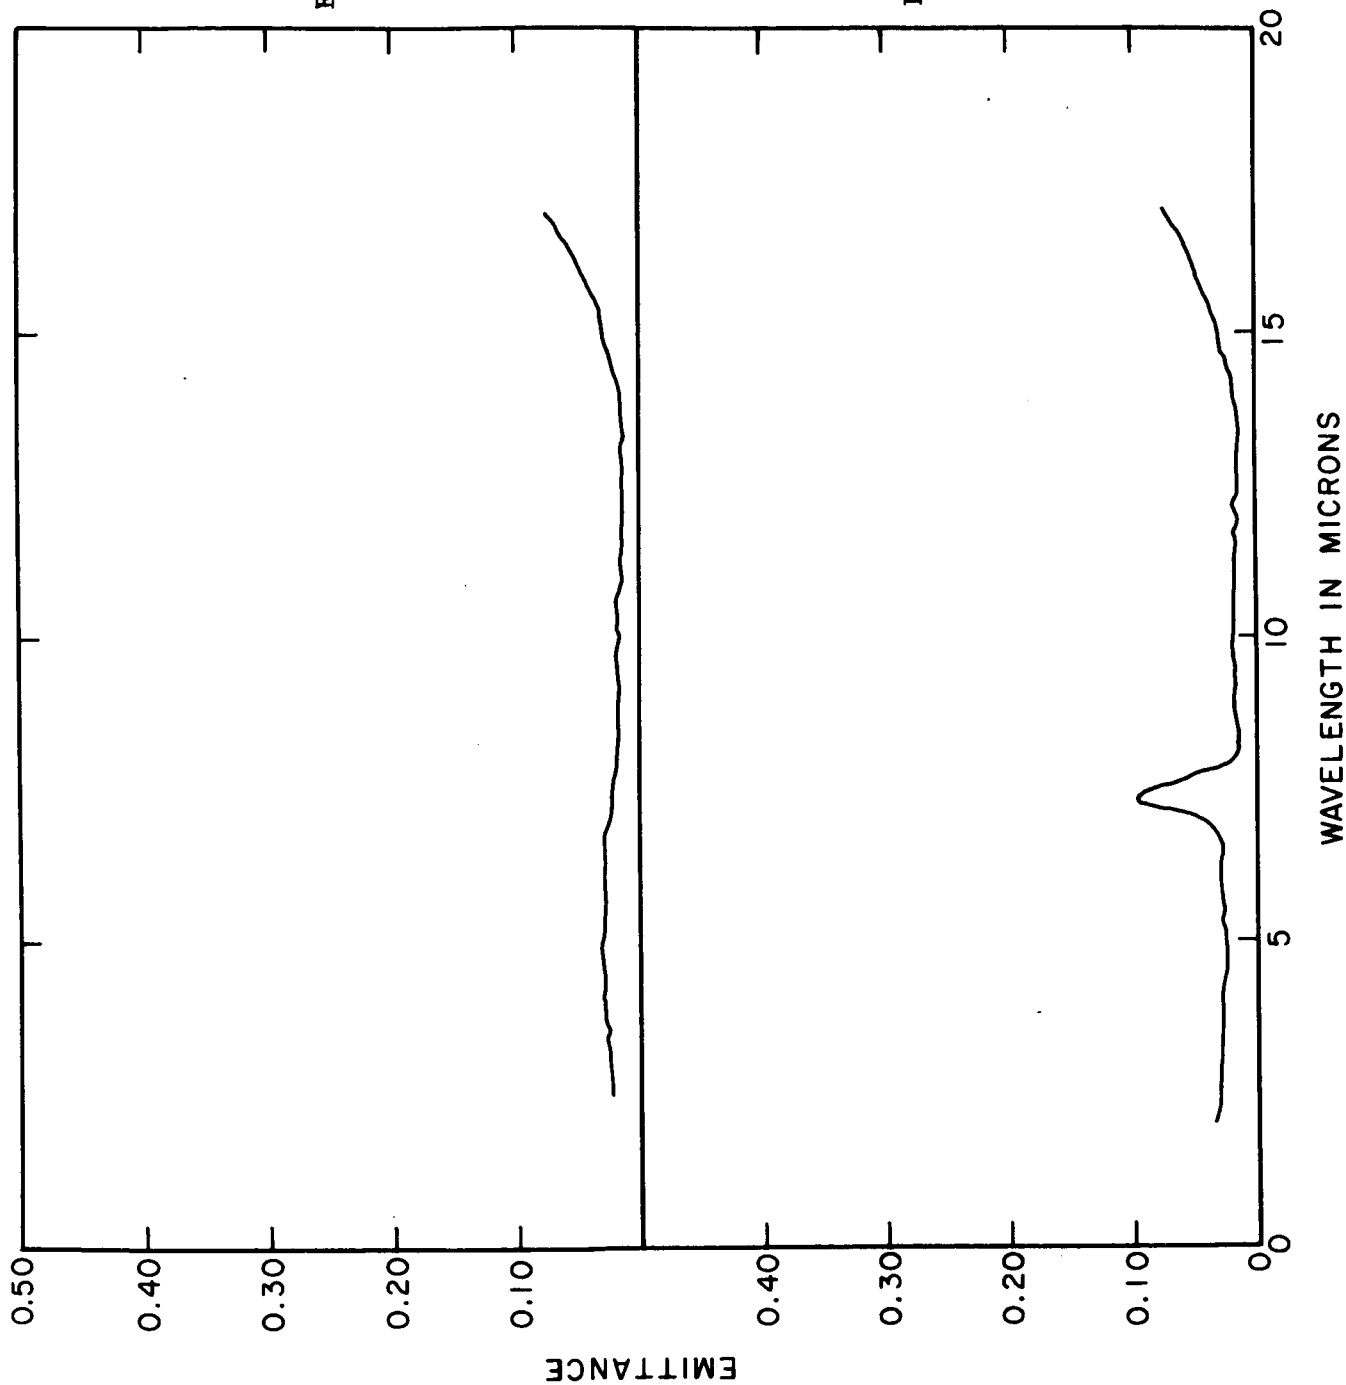

DISTRIBUTION LIST

Commander		National Aeronautics and	
Naval Ordnance Test Station		Space Administration	
China Lake, Calif.		Goddard Space Flight Center	
Attn: M. Peterson	1	Greenbelt, Md.	
Library	1	Attn: Mr. Catoe	1
		L. Dunkelman	1
Barnes Engineering Company		R. Hanel	1
Stamford, Conn.		W. Nordberg	1
Attn: R. DeWaard	1		
		National Aeronautics and	
California Institute of Tech-		Space Administration	
nology,		Washington, D.C. 20546	
1201 E. California St.,		Attn: C. P. Mook, Code RV-1	1
Pasadena 4, Calif.		Dr. W. A. Menzel	1
Attn: I. E. Newland, Reports		R. R. Nash	1
Group JPL	1		
		Director	
E. I. DuPont de Nemours		National Aeronautics and	
& Co., Inc.,		Space Administration	
Engineering Physics Labora-		Ames Research Center	
tory,		Moffett Field, Calif.	
Wilmington, Delaware		Attn: Library	1
Attn: J. K. Barr	1		
		National Aeronautics and	
Lewis Research Center		Space Administration	
21000 Brookpark Road		Flight Research Center	
Cleveland, Ohio		P. O. Box 273	
Attn: J. L. Pollack	1	Edwards, California	
D. A. Otterson	1	Attn: Library	1
M. O. Davies	1		
		Director	
Marshall Space Flight Center		National Aeronautics and	
Huntsville, Ala.		Space Administration	
Attn: G. Heller	1	Langley Research Center	
		Langley Station	
Jet Propulsion Laboratory		Hampton, Va.	
4800 Oak Grove Drive		Attn: Library	1
Pasadena, California			
Attn: R. H. Chase	1	National Aeronautics and	
Mr. Friedman	1	Space Administration	
Mr. Powell	1	Manned Spacecraft Center	
Mr. W. Schade	1	Houston 1, Texas	
W. F. Carroll	1	Attn: Library	1
W. Hovis	1		
Marshall SpaceFlight Center			
Huntsville, Alabama			
Attn: G. Heller	1		

Servo Corporation of
America
111 New South Road
Hicksville, Long Island, N.Y.
Attn: I. Melman

1

NOLC:

J. A. Hart, Code 04	1
C. J. Humphreys, Code 40	1
H. H. Wieder, Code 423	1
R. F. Potter, Code 43	1
J. B. Bernstein, Code 432	1
D. D. Kirk, Code 432	1
D. L. Stierwalt, Code 433	1
G. Zaeschmar, Code 433	1
R. A. Buchanan, Code 433	1
H. H. Caspers, Code 433	1
H. Piller, Code 433	1
C. P. Haber, Code 44	1
F. C. Essig, Code 45	1
Technical Library, Code 234	2